



Research and Development of Novel Advanced Materials for Next- generation Collimators

A. Bertarelli,
G. Arnau Izquierdo, F. Carra, A. Dallochio, M. Gil Costa, N. Mariani

CERN, Geneva, Switzerland

IPAC 2011 – Donostia/San Sebastián, Spain


08.09.2011



What is a (Phase I) LHC collimator

The collimation system must satisfy 2 main functions:

- **Multi-stage Beam Cleaning**, i.e. removing stray particles which would induce quenches in SC magnets.
- **Machine Protection**, i.e. shielding the other machine components from the catastrophic consequences of beam orbit errors.

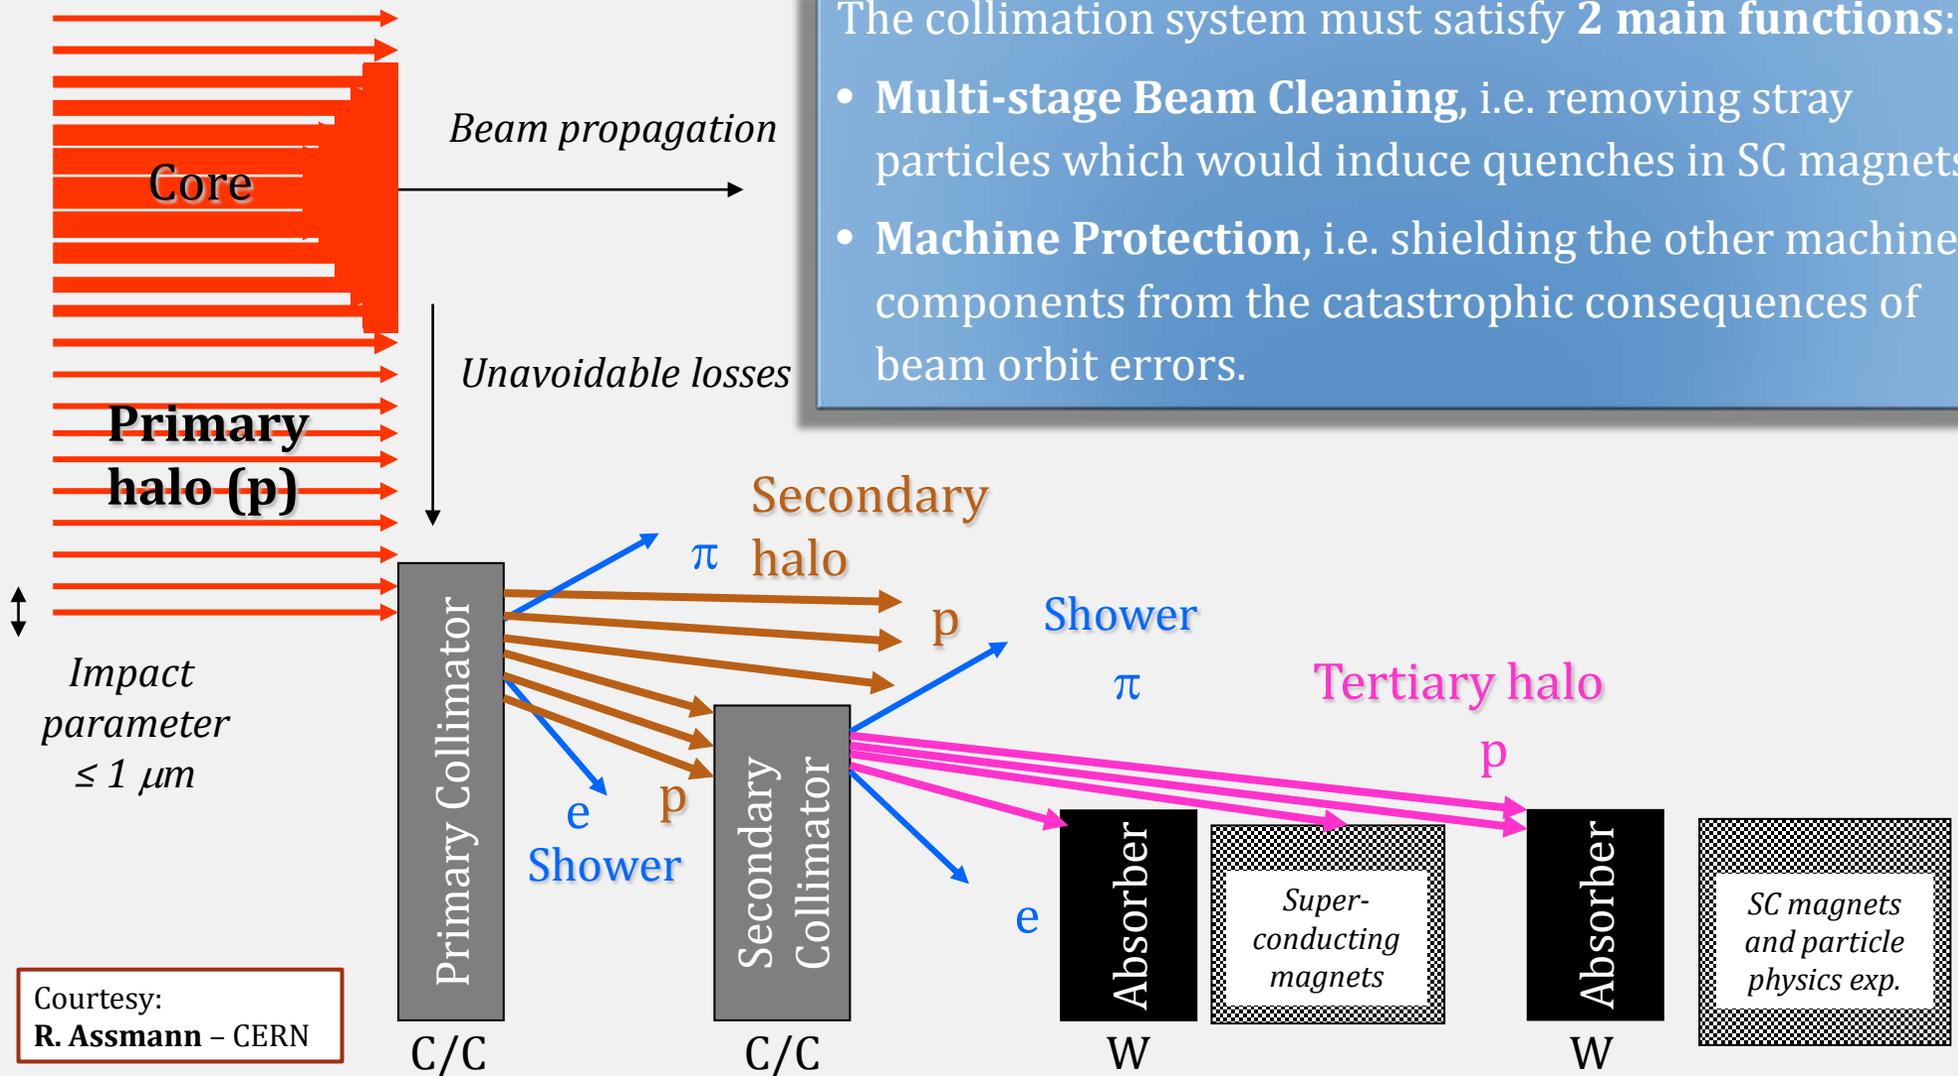


Courtesy:
R. Assmann - CERN



What is a (Phase I) LHC Collimator

- Several types of collimators at multiple locations required.
- Very complex system (100+ LHC Collimators)

Secondary Collimator (TCSG) Cutaway

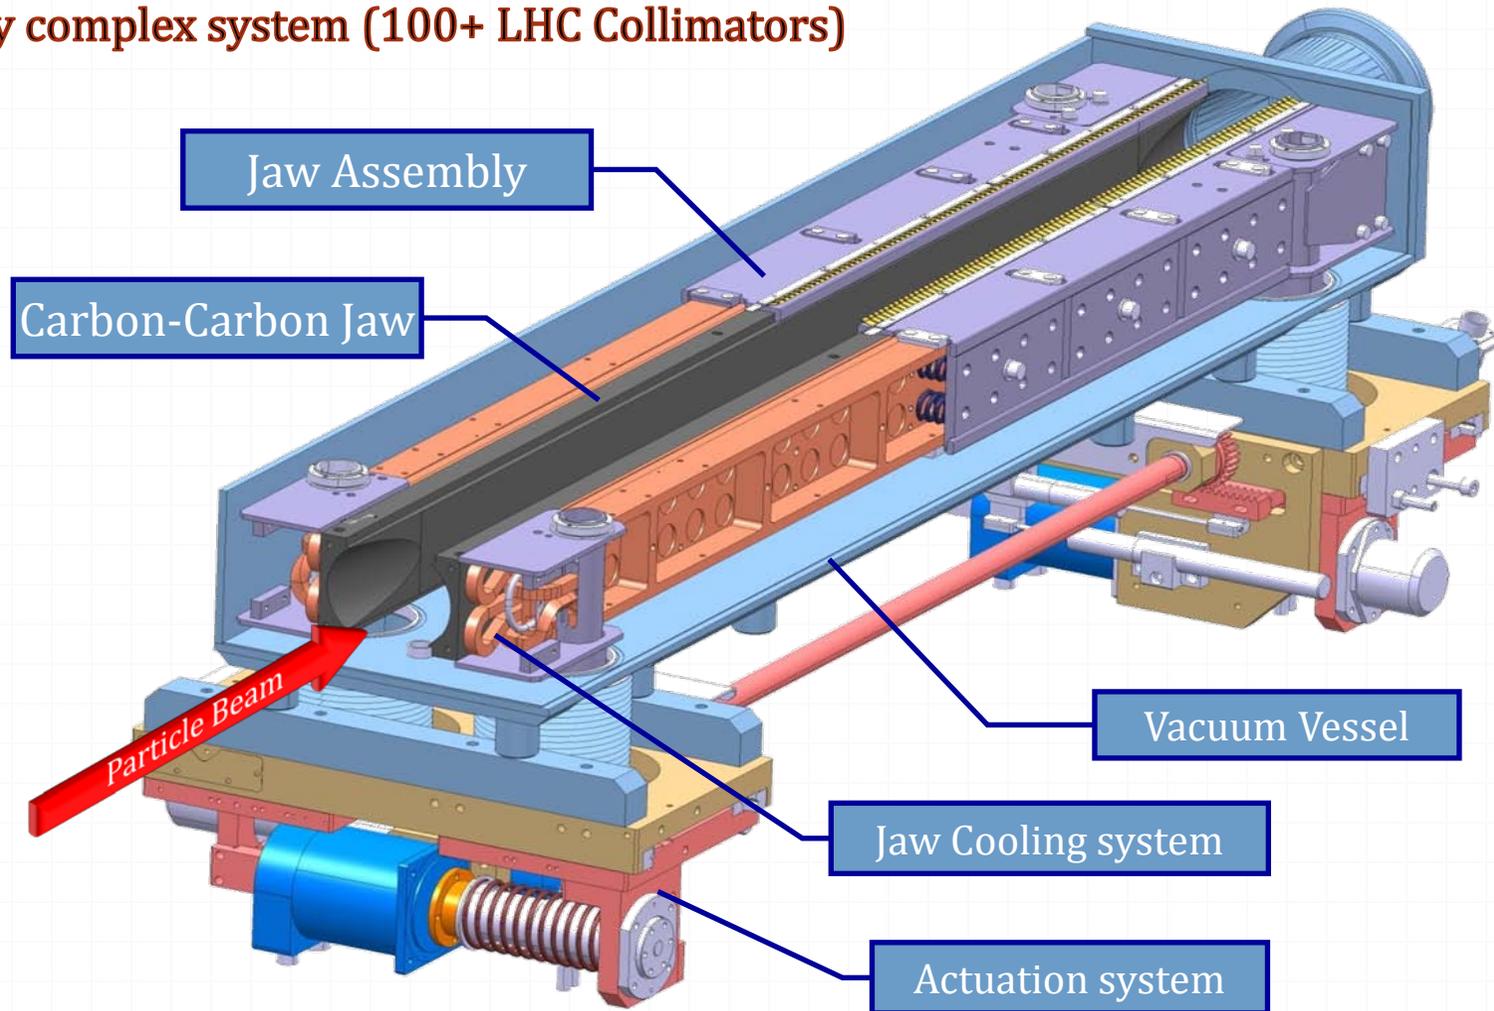



What is a (Phase I) LHC Collimator


Robustness Test at 450 GeV, 3.2×10^{13} protons per shot

- 5 full intensity shots ranging from 1 to 5 mm, 7.2ms ...
- Each impact energy equivalent to more than 1/2 kg of TNT



EN


LHC Phase I Collimation System
Reliable, Robust,
Adequate up to LHC Nominal conditions

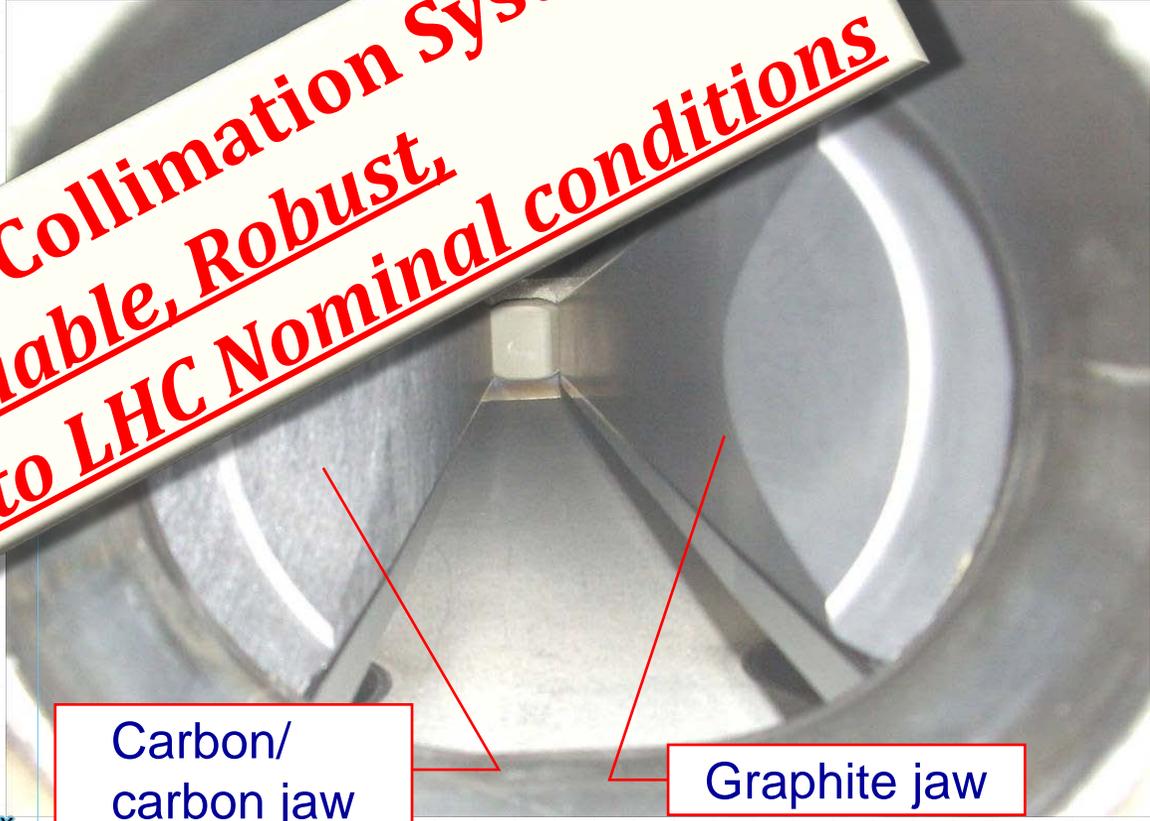

Carbon/
carbon jaw

Graphite jaw

Limits of Phase I Collimators

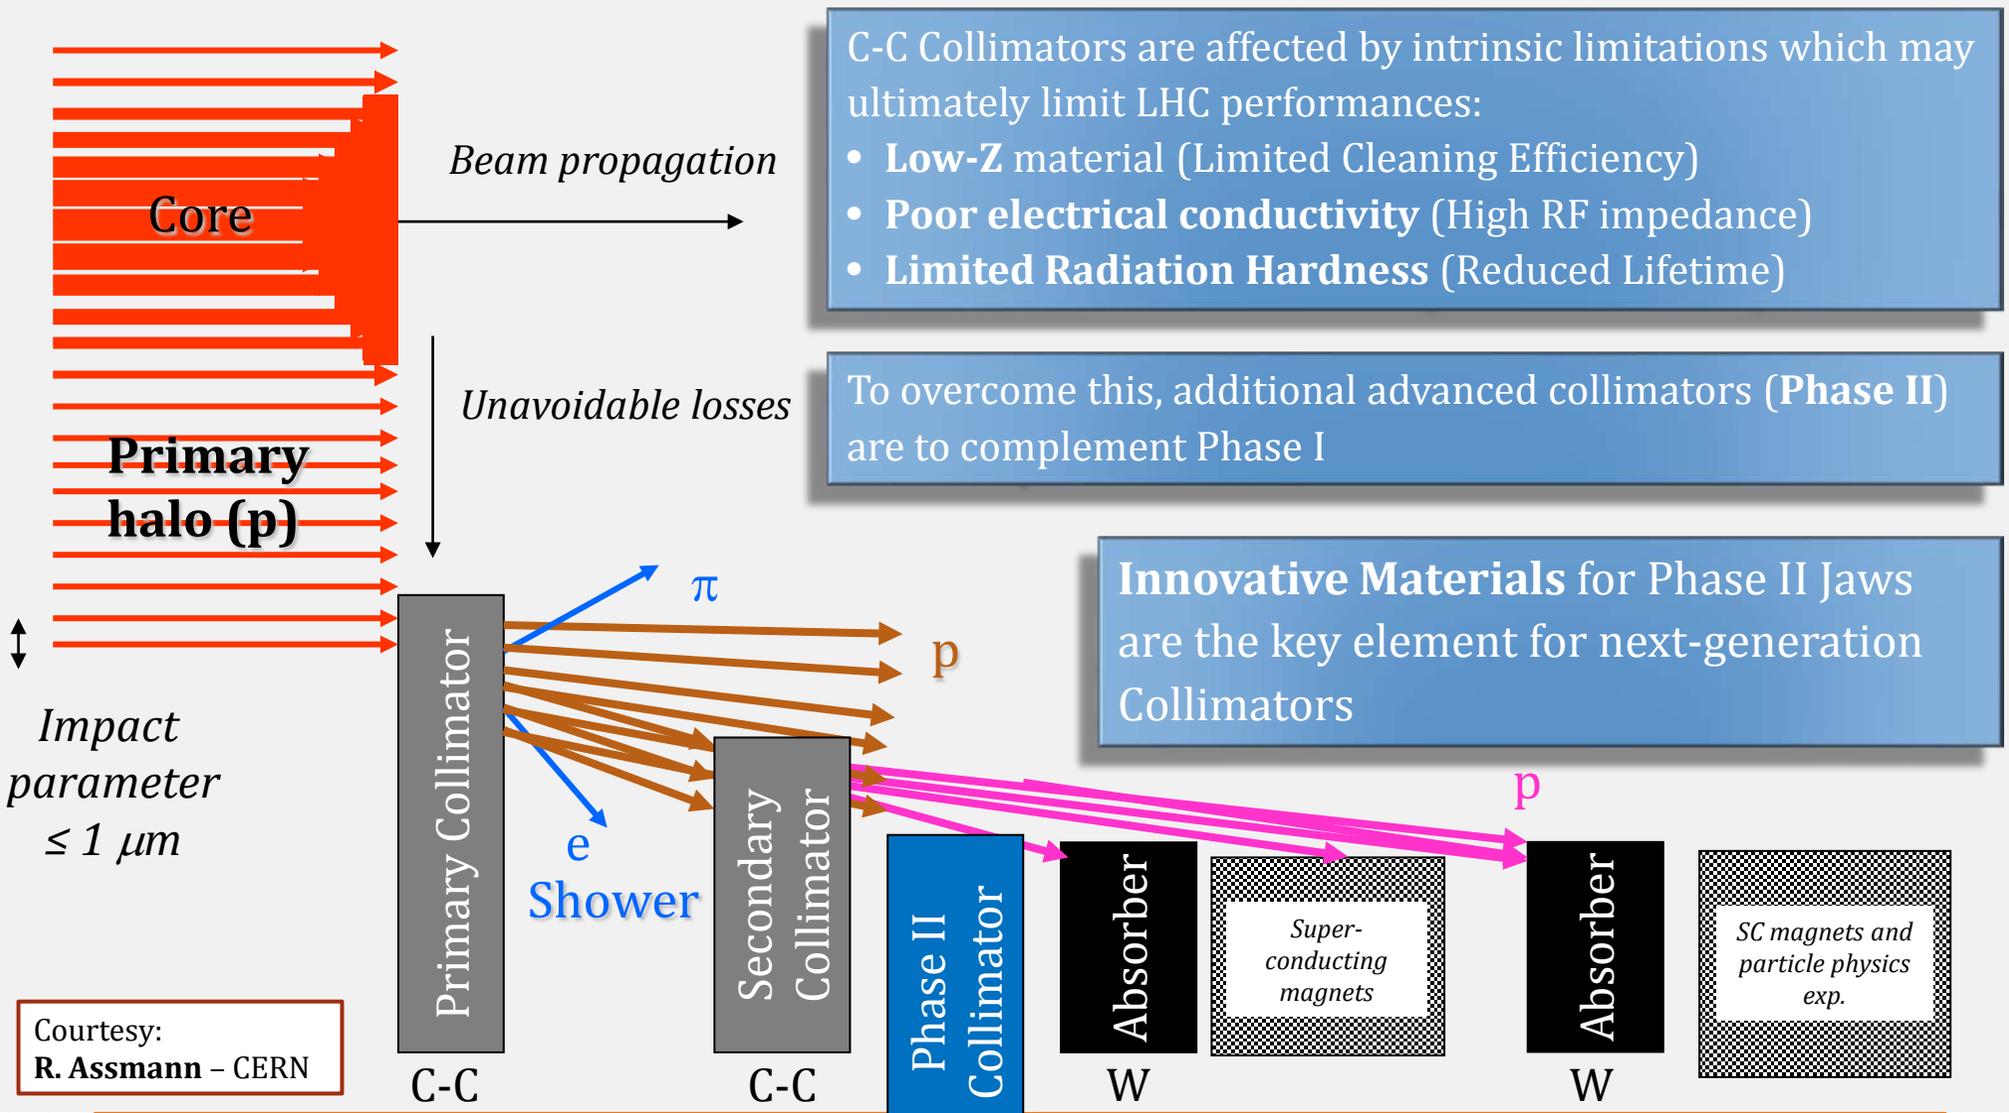

C-C Collimators are affected by intrinsic limitations which may ultimately limit LHC performances:

- **Low-Z material** (Limited Cleaning Efficiency)
- **Poor electrical conductivity** (High RF impedance)
- **Limited Radiation Hardness** (Reduced Lifetime)

To overcome this, additional advanced collimators (**Phase II**) are to complement Phase I

Innovative Materials for Phase II Jaws are the key element for next-generation Collimators

Courtesy:
R. Assmann - CERN

Five Figures of Merit have been identified to classify and rank candidate materials

- **Electrical Conductivity**

Must be maximized to limit RF impedance

- **Steady-state Stability Normalized Index (SSNI)**

Indicates the ability to maintain jaw geometrical stability

- **Transient Thermal Shock Normalized Index (TTSNI)**

Related to highest particle energy (normalized by material properties indicator)

- **Atomic Number (Z)**

(Radiation and

$E\alpha\rho$

Z

T_m

Temperature a material can reach before melting.

“standard” requirements include ...




... Radiation Hardness, UHV Compatibility, Industrial producibility of large components (up to 400x80x25 mm³), Possibility to machine, braze, join, coat ..., Limited brittleness

These indicators are somehow self-conflicting.
A fit-all material does not exist ...
Can we try and combine properties of diverse materials?



Metal-diamond Composites

- **Metal-diamond composites** are advanced thermal management materials combining properties of Diamond (high k , low ρ and low CTE) with those of Metals (**strength**, γ , etc.).
- Sintering techniques include **Rapid Hot Pressing (RHP)**, aka Spark Plasma Sintering (**SPS**), and **Liquid Infiltration**.
- Candidate materials include **Copper-diamond (Cu-CD)**, **Silver-diamond (Ag-CD)** and **Molybdenum-diamond (Mo-CD)**

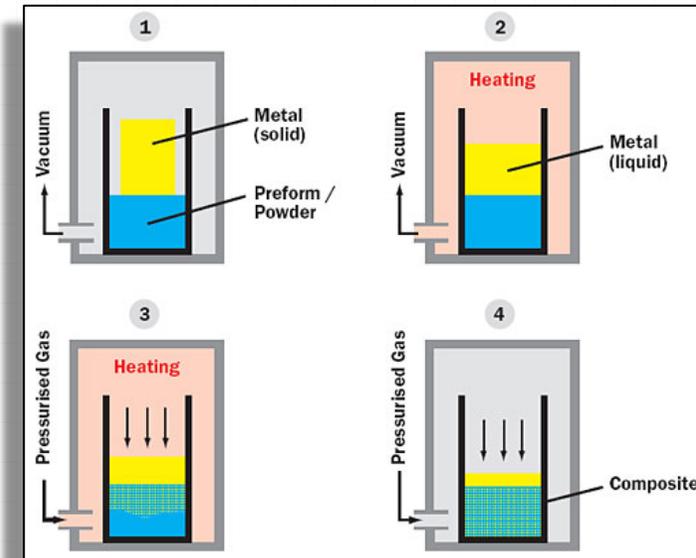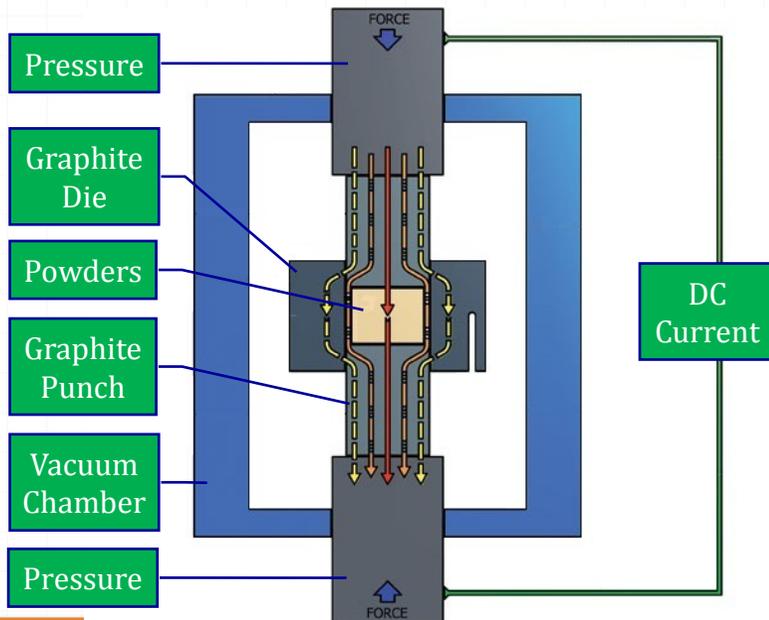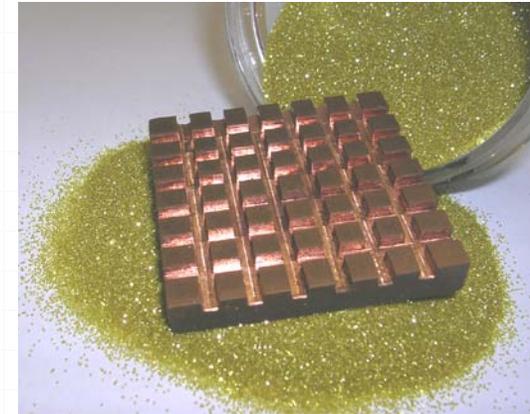



Material Ranking

Material	C-C	Mo	Glidcop®	Cu-CD	Ag-CD	Mo-CD
Density [kg/m ³]	1650	10220	8900	~5400	~6100	~6900
Atomic Number (Z)	6	42	29	~11.4	~22.4	~17.3
T _m [°C]	3650	2623	1083	~1083	~840	~2623
SSNI [kWm ² /kg]	24	2.6	2.5	13.1 ÷ 15.3	11.4 ÷ 15.4	6.9 ÷ 10.9
TSNI [kJ/kg]	793	55	35	44 ÷ 51	60 ÷ 92	72 ÷ 96
Electrical Conductivity [MS/m]	0.14	19.2	53.8	~12.6	~11.8	~9.9

worse



better

- **C-C** stands out as to thermo-mechanical performances. Adversely outweighed by poor electrical conductivity, low Z, expected degradation under irradiation.
- **High-Z metals (Cu, Mo)** possess very good electrical properties. High density adversely affects their thermal stability and accident robustness.
- **Metal-diamond composites** exhibit a balanced compromise between TSNI, SSNI, electrical conductivity, density, atomic number.
- **Mo-CD** limits the consequences of high temperatures induced by very intense beam impacts





- **Cu-CD** developed by **RHP-Technology** (spin-off of Austrian Institute of Technology), Austria
- Characterized in the frame of **EuCARD** / ColMat collaboration

- **R&D objectives:**

- **Geometrical stability**
- **Electrical conductivity**
- **Intermediate density**



- Produced by RHP under $N_2 + H_2$ Atmosphere
- 60% Diamond, 40% Cu
- Small addition of Boron
- Sintering $T \sim 1000^\circ C$
- Good homogeneity and compaction rate ($\sim 95\%$)

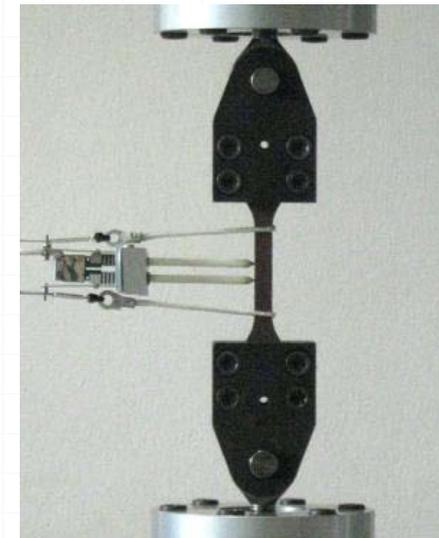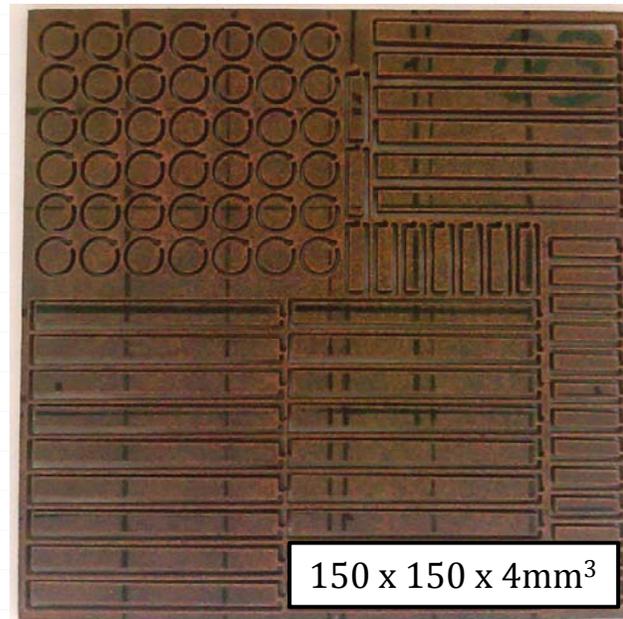

Courtesy: **E. Neubauer,**
M. Kitzmantel – RHP-Tech



Cu-CD Composites

- ↑ No diamond degradation (in reducing atmosphere graphitisation starts at $\sim 1300\text{ }^{\circ}\text{C}$)
- ↑ Good thermal ($\sim 490\text{ W/mK}$) and electrical conductivity ($\sim 12.6\text{ MS/m}$).
- ↓ No direct interface between Cu and CD (lack of affinity). Limited bonding surface assured by Boron Carbides hampers mechanical strength ($\sim 120\text{ MPa}$).
- ↓ BC brittleness adversely affects material toughness.
- ↓ Cu low melting point ($1083\text{ }^{\circ}\text{C}$) limits Cu-CD applications for highly energetic accidents.
- ↓ CTE increases significantly with T due to high Cu content (from $\sim 6\text{ ppmK}^{-1}$ at RT up to $\sim 12\text{ ppmK}^{-1}$ at $900\text{ }^{\circ}\text{C}$)

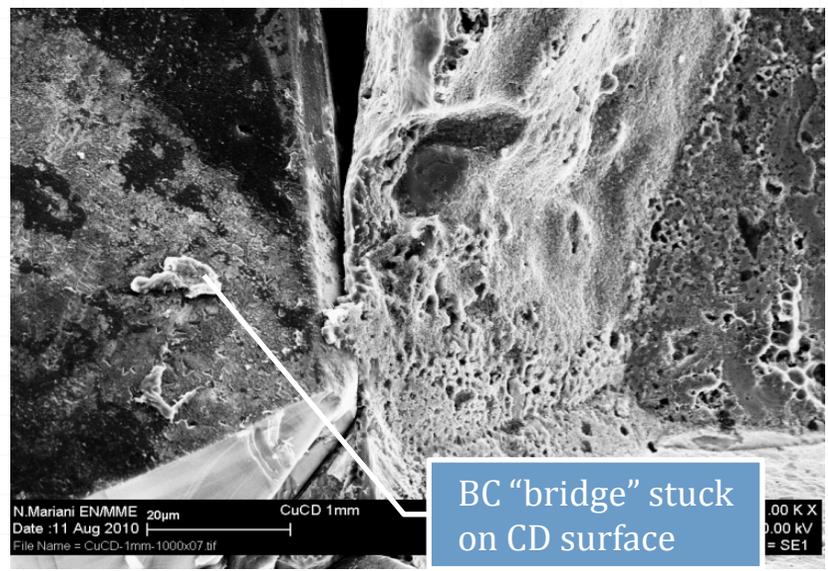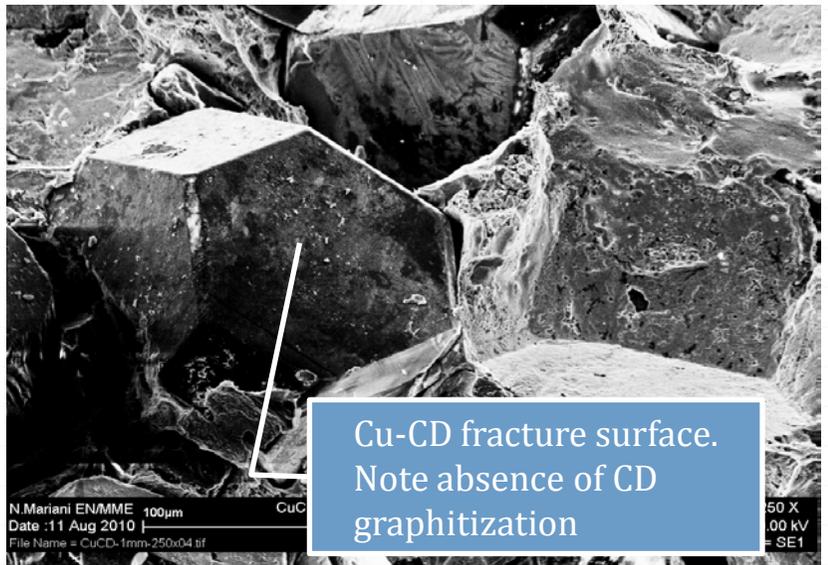

- Developed by **EPFL**, Switzerland.
- Characterized at EPFL and CERN (**EuCARD**).
- Manufactured by Liquid Infiltration of cylindrical samples (Ø100 mm, H 100 mm)
- ~60% Diamond, ~40% Ag-Si alloy

- ↑ Excellent bonding between Ag and CD assured by Silicon Carbides formation on diamond.
- ↑ High Flexural Strength (~**500 MPa**) and toughness.
- ↑ High Electrical Conductivity.
- ↓ Max T_{Service} limited by low-melting eutectic phase Ag-Si (**840 °C**).
- ↓ Hard to manufacture large components (>100 mm)
- ↓ Material non homogeneities due to liquid metal infiltration intrinsic limitations.

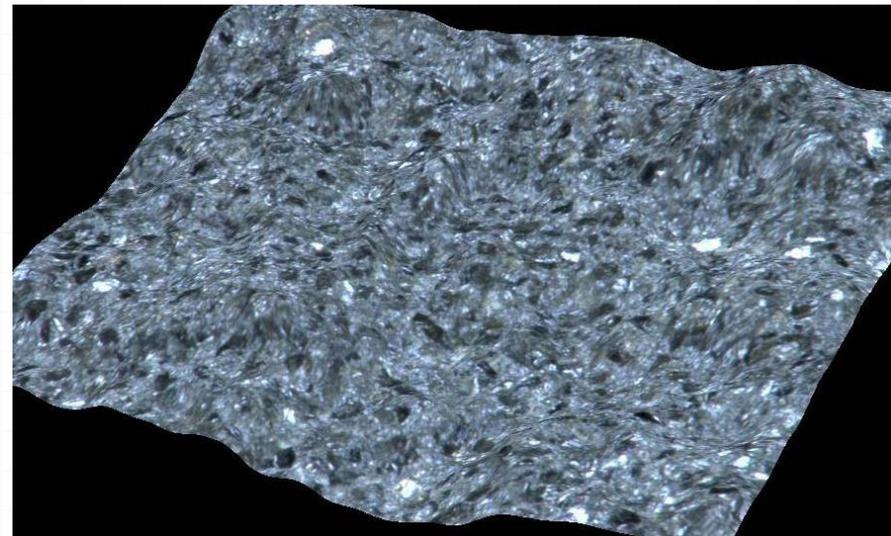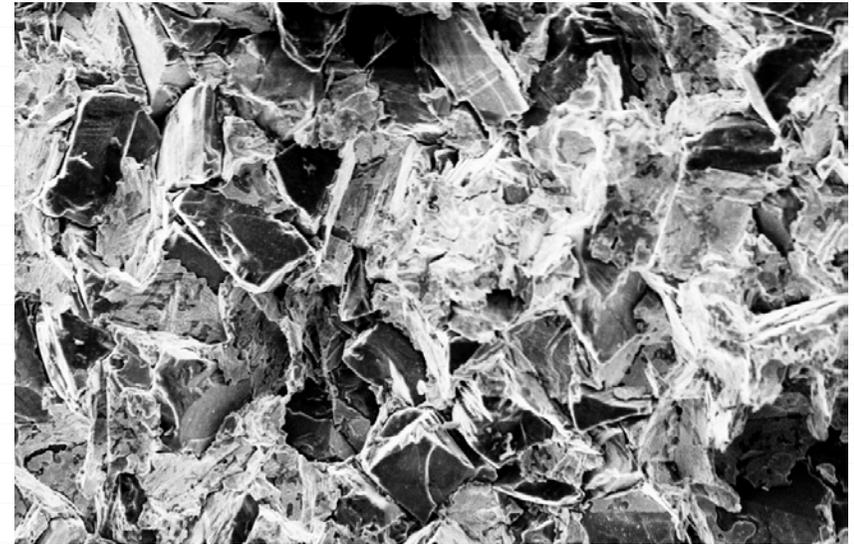



- Co-developed by **CERN** and a SME, **Brevetti Bizz**, Verona, Italy

- **R&D objectives :**

- **Decrease** pure Mo **density** to optimize deposited energy distribution
- Increase **mechanical properties** w.r.t. other Metal-CD
- Increase **thermal stability** and **robustness** at **high temperatures**



- Manufactured through RHP
- Mo and CD create a good interface by forming Mo Carbides.
- Large components can be produced.
- High sintering T of Mo (~**1700 °C**) leads to diamond graphitisation. 2 alternative processes:
 - **Assisted Solid-state Sintering (ASS)**
 - **Liquid Phase Sintering (LPS)**

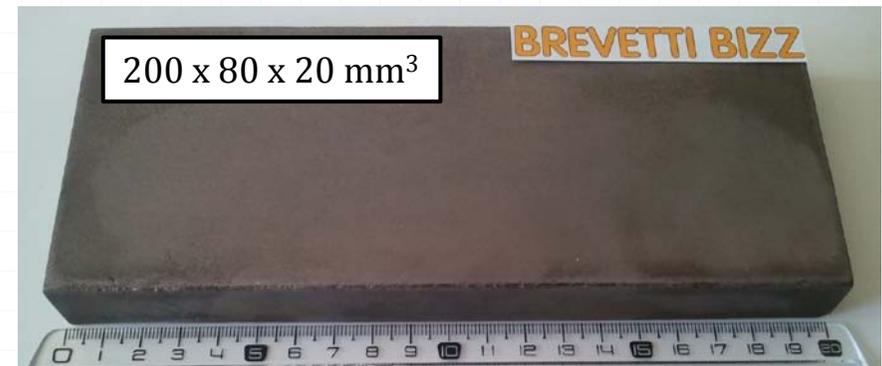
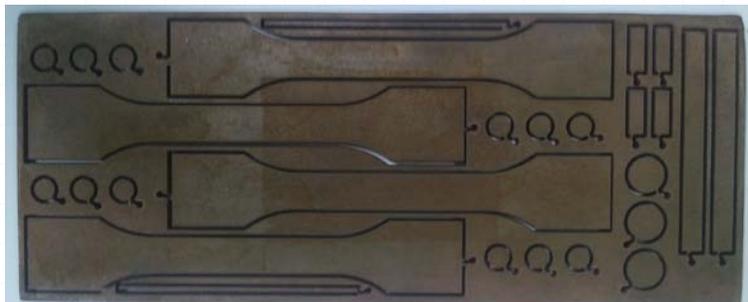


Liquid Phase Sintering (LPS)

- ↑ Addition of low-melting phase (Cu or Cu-Ag) to fill in the pores between Mo and CD
- ↑ Good mechanical strength (400+ MPa) and Thermal Conductivity (185 W/mK)
- ↓ Max T_{Service} limited by low-melting phase (Cu)


Assisted Solid-state Sintering (ASS)

- ↑ Addition of small amounts of activating elements (Ni, Pd) enhances Mo sintering at low T (~1300 °C)
- ↑ Absence of low-melting phase increases service T up to ~2600 °C
- ↓ Large diamond particles interfere with Mo compaction.
- ↓ Diamond graphitization not fully avoided.

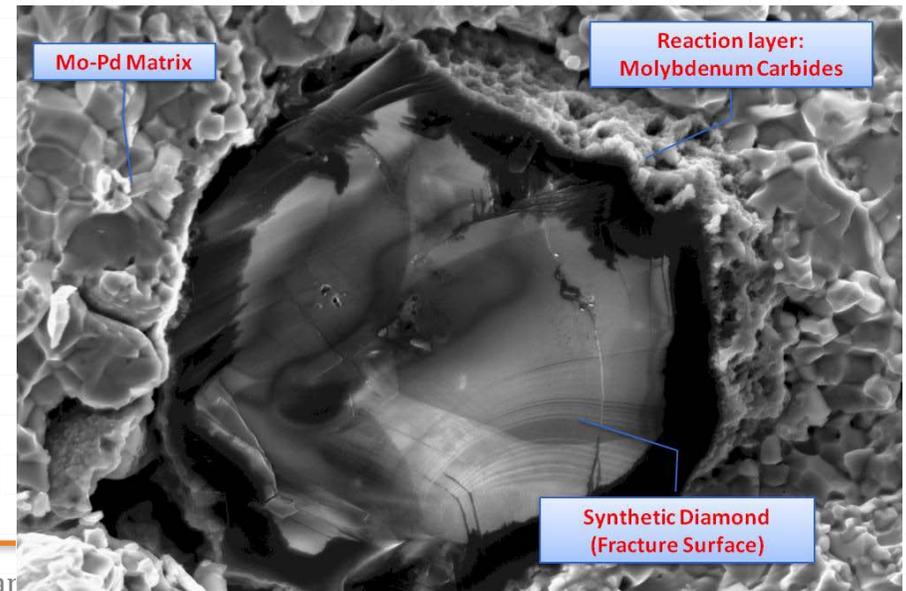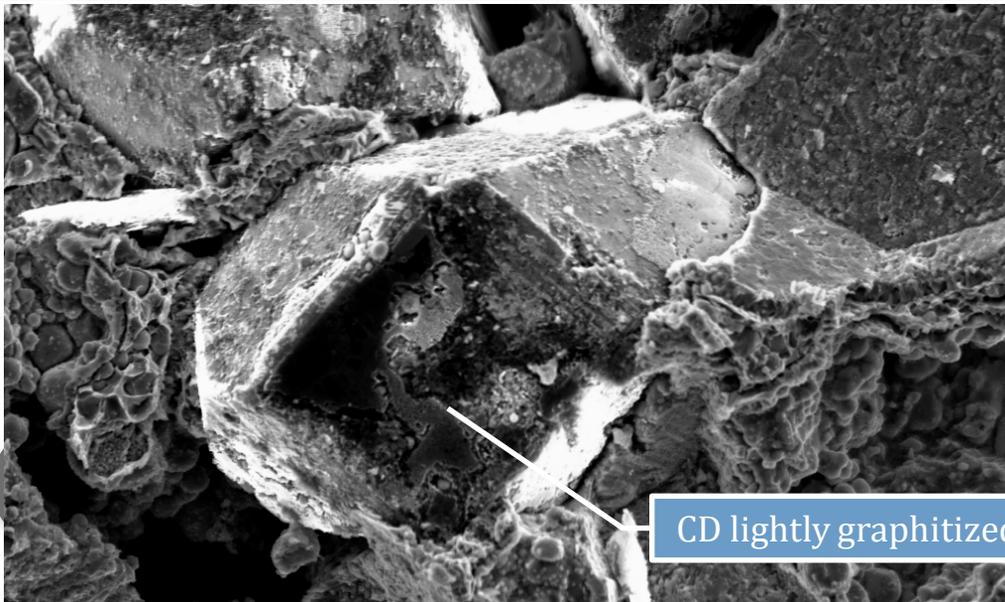

Studied material comparison

- A single, comprehensive comparison of characterized materials is proposed on the basis of normalized Figures of Merit.
- Needless to say, any choice of Figures of Merit, of their combination and target values is arbitrary ...
- This said, this comparison confirms that Mo-CD is, so far, the best candidate.

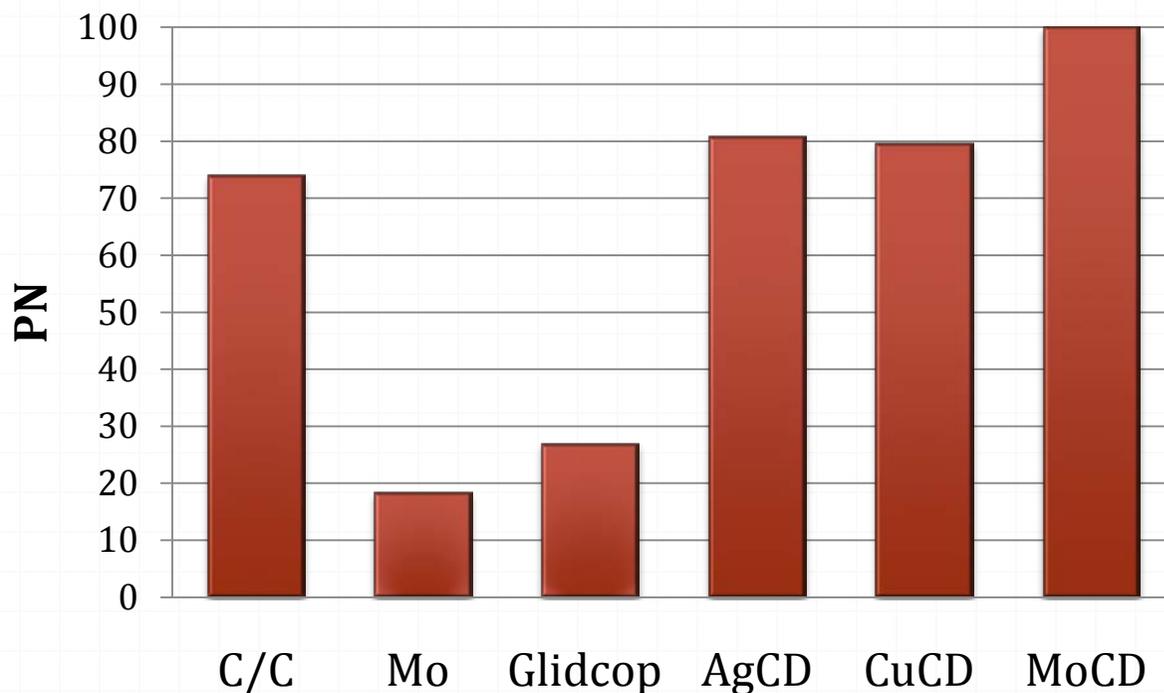

$$Pn_i = [P_i / \text{Max}(P)]$$

$$Pn_z = 1 - \left(\frac{|Z - 12|}{42} \right)$$



$$PN = \frac{\prod Pn_i}{\text{Max}(\prod Pn_i)}$$






Simulations and Testing

RUSSIAN RESEARCH CENTRE
KURCHATOV INSTITUTE

- **Irradiation damage tests** at RRC-KI and GSI.
- Preliminary results from GSI on Cu-CD show no degradation of Cu/CD interface. Defects in CD lattice seem to occur.
- **Advanced simulations** being performed at CERN and Polito on materials under extreme conditions.
- Beam tests in CERN's **HiRadMat** to experimentally assess material models.

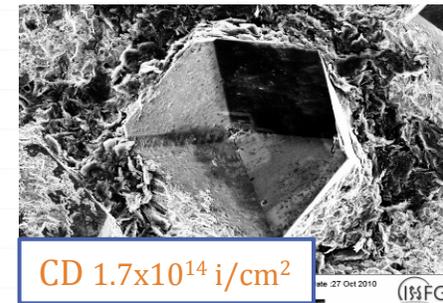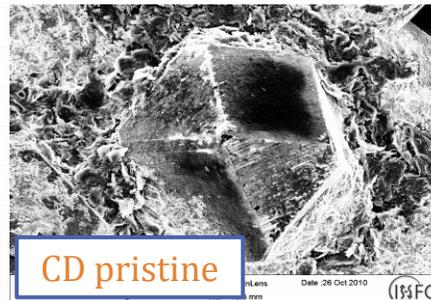

Courtesy: M. Tomut - GSI

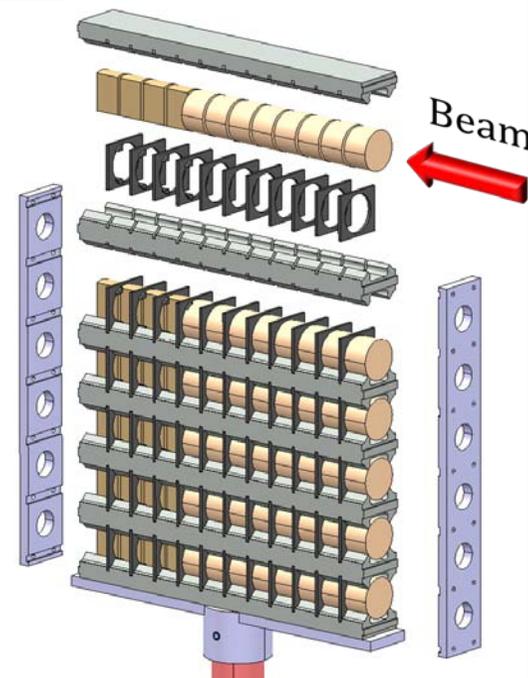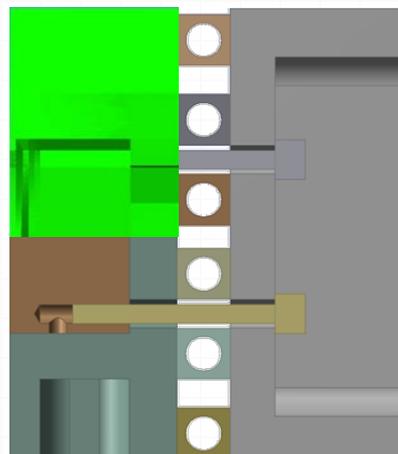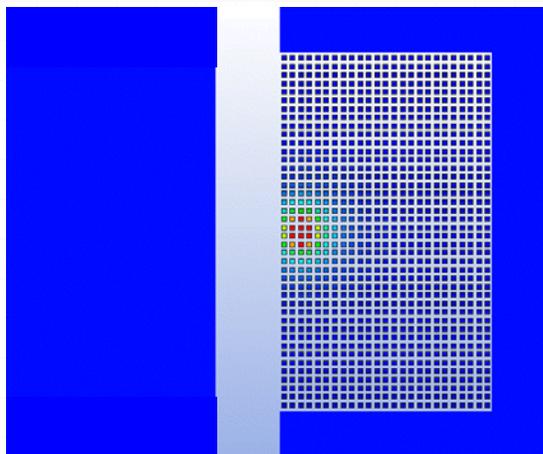



Conclusions

- Bringing LHC beyond nominal performances might require new generation collimators embarking novel advanced materials.
- Metal-diamond composites are particularly appealing as they promise to combine diamond and metal properties.
- Figures of Merit were defined, allowing to pinpoint “best” candidates and to set ambitious goals.
- An intense R&D program has been launched at CERN with partners partly within the EuCARD collaboration
- Cu-CD, Mo-CD and Ag-CD were studied and successfully produced. Size challenge has been met for Cu-CD and Mo-CD.
- A large characterization effort has been carried out: a magic material does not exist, but Mo-CD seems to stand out as a balanced compromise between key parameters.
- Radiation hardness assessment is ongoing for selected materials. Beam tests under extreme conditions are foreseen at CERN’s HiRadMat facility.
- The R&D program is still in full progress.





Acknowledgements

BREVETTI BIZZ

RUSSIAN RESEARCH CENTRE
KURCHATOV INSTITUTE 

This work would have been impossible without the contributions of many people:

S. Bizzaro, *Brevetti Bizz*

R. Assmann, E. Berthomé, V. Boccone, F. Cerutti, M. Guinchard, *CERN*

L. Weber, *EPFL*

M. Tomut, *GSI*

L. Peroni, M. Scapin, *Politecnico di Torino*

M. Kitzmantel, E. Neubauer, *RHP-Technology*



A. Ryazonov, *RRC-Kurchatov Institute*